

Fabrication of Fiber-Reinforced Celsian Matrix Composites

Narottam P. Bansal
Glenn Research Center, Cleveland, Ohio

John A. Setlock
Case Western Reserve University, Cleveland, Ohio

The NASA STI Program Office . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) Program Office plays a key part in helping NASA maintain this important role.

The NASA STI Program Office is operated by Langley Research Center, the Lead Center for NASA's scientific and technical information. The NASA STI Program Office provides access to the NASA STI Database, the largest collection of aeronautical and space science STI in the world. The Program Office is also NASA's institutional mechanism for disseminating the results of its research and development activities. These results are published by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA's counterpart of peer-reviewed formal professional papers but has less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.

- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or cosponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services that complement the STI Program Office's diverse offerings include creating custom thesauri, building customized data bases, organizing and publishing research results . . . even providing videos.

For more information about the NASA STI Program Office, see the following:

- Access the NASA STI Program Home Page at **<http://www.sti.nasa.gov>**
- E-mail your question via the Internet to **help@sti.nasa.gov**
- Fax your question to the NASA Access Help Desk at (301) 621-0134
- Telephone the NASA Access Help Desk at (301) 621-0390
- Write to:
NASA Access Help Desk
NASA Center for Aerospace Information
7121 Standard Drive
Hanover, MD 21076



Fabrication of Fiber-Reinforced Celsian Matrix Composites

Narottam P. Bansal
Glenn Research Center, Cleveland, Ohio

John A. Setlock
Case Western Reserve University, Cleveland, Ohio

Prepared for the
“Processing of Fibers and Composites” Conference
Castelvecchio Pascoli, Italy, May 21–26, 2000
sponsored by the United Engineering Foundation, New York

National Aeronautics and
Space Administration

Glenn Research Center

Acknowledgments

Thanks are due to Rob Dickerson, Terry Kacik, Ron Phillips and Ralph Garlick for technical assistance during this research.

Trade names or manufacturers' names are used in this report for identification only. This usage does not constitute an official endorsement, either expressed or implied, by the National Aeronautics and Space Administration.

Available from

NASA Center for Aerospace Information
7121 Standard Drive
Hanover, MD 21076
Price Code: A03

National Technical Information Service
5285 Port Royal Road
Springfield, VA 22100
Price Code: A03

FABRICATION OF FIBER-REINFORCED CELSIAN MATRIX COMPOSITES

Narottam P. Bansal
National Aeronautics and Space Administration
Glenn Research Center
Cleveland, Ohio 44135

John A. Setlock
Department of Materials Science and Engineering
Case Western Reserve University
Cleveland, Ohio 44106

SUMMARY

A method has been developed for the fabrication of small diameter, multifilament tow fiber reinforced ceramic matrix composites. Its application has been successfully demonstrated for the Hi-Nicalon/celsian system. Strong and tough celsian matrix composites, reinforced with BN/SiC-coated Hi-Nicalon fibers, have been fabricated by infiltrating the fiber tows with the matrix slurry, winding the tows on a drum, cutting and stacking of the prepreg tapes in the desired orientation, and hot pressing. The monoclinic celsian phase in the matrix was produced *in situ*, during hot pressing, from the 0.75BaO-0.25SrO-Al₂O₃-2SiO₂ mixed precursor synthesized by solid state reaction from metal oxides. Hot pressing resulted in almost fully dense fiber-reinforced composites. The unidirectional composites having ~42 vol % of fibers exhibited graceful failure with extensive fiber pullout in three-point bend tests at room temperature. Values of yield stress and strain were 435±35 MPa and 0.27±0.01 percent, respectively, and ultimate strengths of 900±60 MPa were observed. The Young's modulus of the composites was measured to be 165±5 GPa.

INTRODUCTION

Monoclinic celsian BaAl₂Si₂O₈ (BAS) and SrAl₂Si₂O₈ (SAS) are refractory materials having melting points higher than 1700 °C. These materials are resistant to oxidation and reduction and also show reasonably good resistance to alkali attack. These materials are phase stable up to ~1600 °C and chemically compatible with alumina, mullite and silicon nitride (in inert or nitrogen atmospheres) at elevated temperatures. They show low values of dielectric constant and loss tangent which make them promising materials for electromagnetic windows or radome applications (ref. 1) at high temperatures, packaging for microelectronics, high voltage condensers and other electric insulating products. Celsian is also useful as an environmental barrier coating for SiC_f/SiC composites and protects against the loss of silica as volatile silicon hydroxide species in the combustion products in turbine engines at elevated temperatures (ref. 2). Celsian is also being investigated as a matrix material for fiber-reinforced composites (refs. 3 to 6) for high temperature structural applications in hot sections of turbine engines.

BAS exists in three different polymorphs, the monoclinic, hexagonal, and orthorhombic phases. The monoclinic phase, commonly known as celsian, is the naturally occurring phase. The hexagonal phase, also known as hexacelsian, and the orthorhombic phase are found only in synthetic products. The hexacelsian phase is thermodynamically stable at temperatures between 1590 °C and the melting point whereas the celsian phase is stable at temperatures below 1590 °C. However, hexacelsian can exist as a metastable phase at all temperatures from 1590 °C to room temperature. At ~300 °C, hexacelsian undergoes a rapid, reversible structural transformation (ref. 7) into the orthorhombic form, accompanied by a large volume change of ~3 percent. Thus, hexacelsian is an undesirable phase.

In both the BAS and SAS systems, hexacelsian is always the first phase to form. However, on heat treatment at ~1200 °C or higher temperatures, its transformation into the monoclinic phase is very sluggish in BAS (ref. 8) and very rapid in SAS (ref. 9). It is known that doping of BAS with SAS accelerates the hexacelsian to monoclinic celsian transformation (ref. 10). Fortunately, BAS and SAS form solid solutions in the entire composition range (refs. 1 and 10). The starting composition of 0.75BaO-0.25SrO-Al₂O₃-2SiO₂ (BSAS) was used for the synthesis of monoclinic celsian in the present study.

Processing and properties of celsian glass-ceramic matrix composites reinforced with large diameter CVD SiC SCS-6 monofilaments (refs. 3 to 6) and the multifilament small diameter Nicalon (ref. 11) and HPZ (ref. 12) fibers have been described earlier. The objective of this study was to develop the fabrication of small diameter, multifilament tow fiber-reinforced celsian matrix composites. Microstructures of the resulting FRCs were characterized and room temperature mechanical properties were measured. Strong, tough, and almost fully dense composites reinforced with BN/SiC-coated, Hi-Nicalon fibers have been obtained.

MATERIALS AND EXPERIMENTAL PROCEDURE

The matrix of 0.75BaO-0.25SrO- Al_2O_3 -2SiO₂ (BSAS) composition was synthesized by a solid-state reaction method (ref. 13). The starting materials used were BaCO₃ (Alfa Products), SrCO₃ (Alfa Products), Al₂O₃ (Baikowski International Corp., high purity CR 30), and SiO₂ (Cerac Inc., 99.9 percent purity, -325 mesh) powders. Appropriate quantities of various powders were slurry mixed in acetone and ball milled for ~24 hr using alumina milling media. Acetone was then evaporated and a part of the mixture was subjected to thermogravimetric analysis (TGA) in air. The oxide mixed powder was calcined at ~900 to 920 °C for decomposition of the carbonates into oxides, followed by cooling to room temperature and grinding. A small part of the calcined powder was loaded into a graphite die and hot pressed at 1300 °C for 2 to 3 hr under 27.5 MPa (4 ksi) pressure.

Polymer derived Hi-Nicalon fiber tows (1800 denier, 500 filaments/tow) with low oxygen content produced by Nippon Carbon Co. were used as the reinforcement. These fibers have an average diameter of ~14 μm; a reported (refs. 14 and 15) chemical composition (wt %) of 62.4%Si, 37.1%C, and 0.5%O; and C/Si atomic ratio of ~1.39. The Hi-Nicalon fibers mainly consist of SiC microcrystals with an average grain size of 4 nm and amorphous carbon. These fibers have a density of 2.7 g/cm³, room temperature tensile strength of ~2.8 GPa, elastic modulus of 270 GPa, and an average coefficient of thermal expansion of $3.5 \times 10^{-6}/^\circ\text{C}$ from room temperature to 500 °C. Hi-Nicalon fibers having a dual surface layer of BN overcoated with SiC were used in the present study. The fiber coatings were applied by a commercial vendor using a continuous chemical vapor deposition (CVD) reactor. The BN coating was deposited at ~1000 °C utilizing a proprietary precursor and was amorphous to partly turbostratic in nature. A thin overcoating of SiC was also deposited by CVD onto the BN-coated fibers. The SiC layer was crystalline. The nominal coating thicknesses were 0.4 μm for BN and 0.3 μm for SiC. The BN interfacial layer acts as a weak, crack-deflecting phase, while the SiC overcoat acts as a barrier to diffusion of boron from BN into the oxide matrix and also prevents diffusion of matrix elements into the fiber.

A sketch of the set-up used for infiltration of the matrix slurry into the fiber tows is shown in figure 1. This is similar to the set-up reported earlier by Prewo (ref. 16). BSAS powder that had been calcined at 900 to 920 °C for 20 to 24 hr was made into a slurry by dispersing it in methyl ethyl ketone along with organic additives as binder, surfactant, deflocculant and plasticizer followed by ball milling. Tows of BN/SiC-coated Hi-Nicalon fibers were spread using rollers and coated with the matrix precursor by passing through the slurry. Excess slurry was squeezed out of the fiber tow before winding at 0.977 mm tow spacing (26 fiber tows/in.) on a rotating drum. After drying, the prepreg tape was cut to size. Unidirectional fiber-reinforced composites were prepared by tape lay up (12 plies) followed by warm pressing at ~150 °C to form a “green” composite. The fugitive organics were slowly burned out of the sample in air at ~500 °C, followed by hot pressing under vacuum in a graphite die. Mée hot pressed fiber-reinforced composite panel was surface polished and sliced into test bars (~50.4×6.4×1.9 mm) for mechanical testing.

Thermogravimetric analysis (TGA) of the calcination process was carried out at a heating rate of 5 °C/min under flowing air (~60 ml/min) from room temperature to 1500 °C using a Perkin-Elmer TGA-7 system which was interfaced with a computerized data acquisition and analysis system. X-ray diffraction (XRD) patterns were recorded at room temperature using a step scan procedure (0.02°/2θ step, time per step 0.5 or 1 sec) on a Philips ADP-3600 automated diffractometer equipped with a crystal monochromator employing Cu K_α radiation. Density was measured from dimensions and mass as well as by the Archimedes method. Microstructures of the polished cross-sections and fracture surfaces were observed in an optical microscope as well as in a JEOL JSM-840A scanning electron microscope (SEM). For transmission electron microscopy (TEM), thin foils of the composite samples were prepared by slicing, polishing, dimple grinding, and argon ion beam milling. A thin carbon coating was evaporated onto the TEM thin foils and the SEM specimens for electrical conductivity prior to analysis. The thin foils were examined in a Philips EM400T operating at 120 keV. X-ray elemental analyses on the TEM were acquired using a Kevex thin window energy dispersive spectrometer (EDS) and analyzer. Mechanical properties were determined from stress-strain curves recorded in three-point flexure using an Instron 4505 universal testing instrument at a crosshead speed of 1.27 mm/min (0.05 in./min) and support span

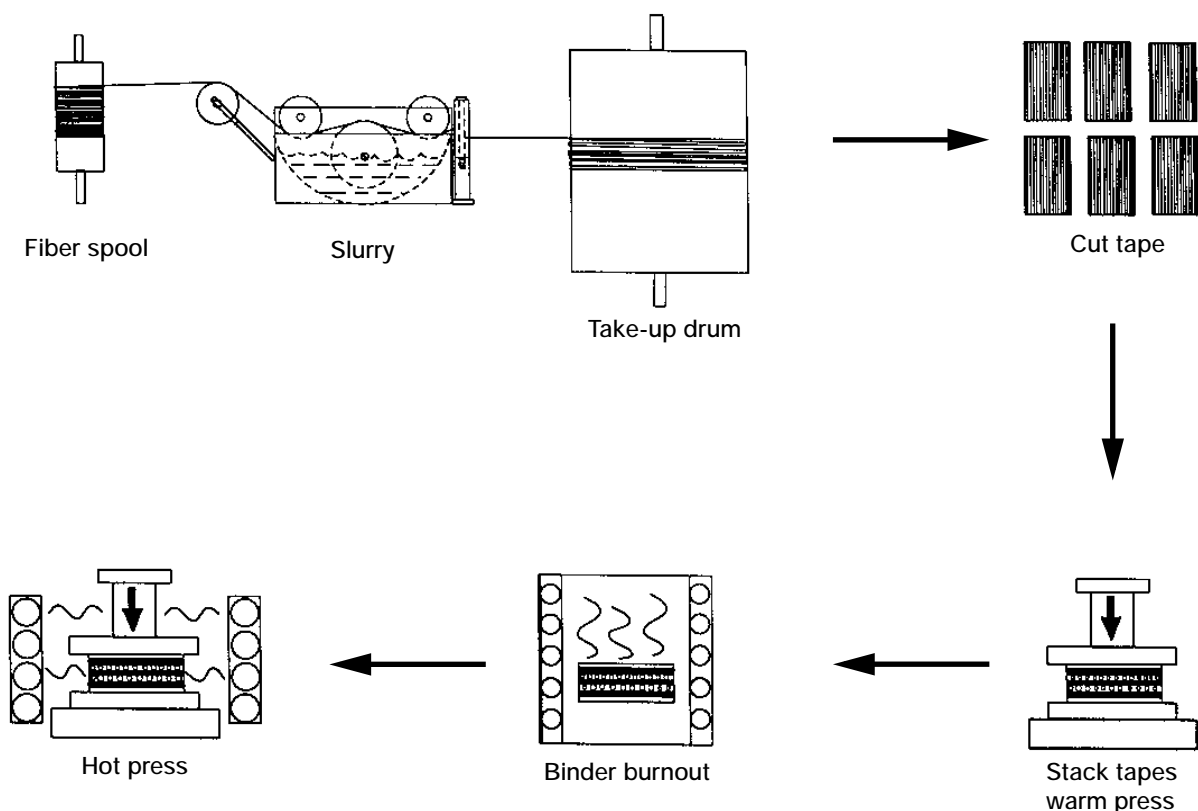


Figure 1.—Schematic of the set-up used for fabrication of small diameter multifilament fiber tow reinforced ceramic composites by matrix slurry infiltration and hot pressing.

(L) of 40 mm. Strain gauges were glued to the tensile surfaces of the flexure test bars. Stress was calculated using beam theory. The yield stress was calculated from the stress-strain curves from the point where the curve deviates from linearity. Elastic modulus of the composite was determined from the linear portion of the stress-strain curve up to the yield point using linear interpolation.

RESULTS AND DISCUSSION

The TGA curve of the mixed BSAS powder consisting of metal carbonates and oxides is shown in figure 2. Minor weight loss near room temperature is due to evaporation of the residual moisture and acetone. A major event showing a large weight loss, due to the decomposition of barium and strontium carbonates into oxides, is observed between ~750 to 1000 °C. A calcination temperature of 900 to 920 °C was chosen for decomposition of the carbonates. The mixed powder was calcined at this temperature for 20 to 24 hr in air. TGA analysis of this calcined powder showed no further weight loss indicating complete decomposition of the metal carbonates during the calcination step.

The XRD pattern of the mixed powder, calcined at ~915 °C for 20 hr in air, is presented in figure 3. SiO_2 (α -quartz) and BaAl_2O_4 were the major phases present. Small amounts of Ba_2SiO_4 , $\alpha\text{-Al}_2\text{O}_3$, and $\text{Ba}_2\text{Sr}_2\text{Al}_2\text{O}_7$ were also identified. Figure 4 shows the XRD pattern taken from the surface of a monolithic sample made by hot pressing the precalcined powder at 1300 °C for 2 hr under 27.5 MPa (4 ksi). All the XRD peaks correspond to the monoclinic celsian phase with complete absence of the undesirable hexacelsian phase.

SEM micrographs showing the surface and the cross-sections of the BN/SiC coated Hi-Nicalon fibers are given in figure 5. The coatings on some of the fibers appear to be smooth and of uniform thickness whereas on other fibers the coating is very thick and granular. SEM micrographs taken from the polished cross-sections of the fibers are shown in figure 6. The double coating on the fiber surface is clearly visible. The dark layer is BN and the bright layer is SiC.

Some of the composite physical characteristics are given in table I. The fiber volume fraction in the composites was calculated to be ~42 percent. From their densities, the composites appear to be almost fully dense. The XRD pattern taken

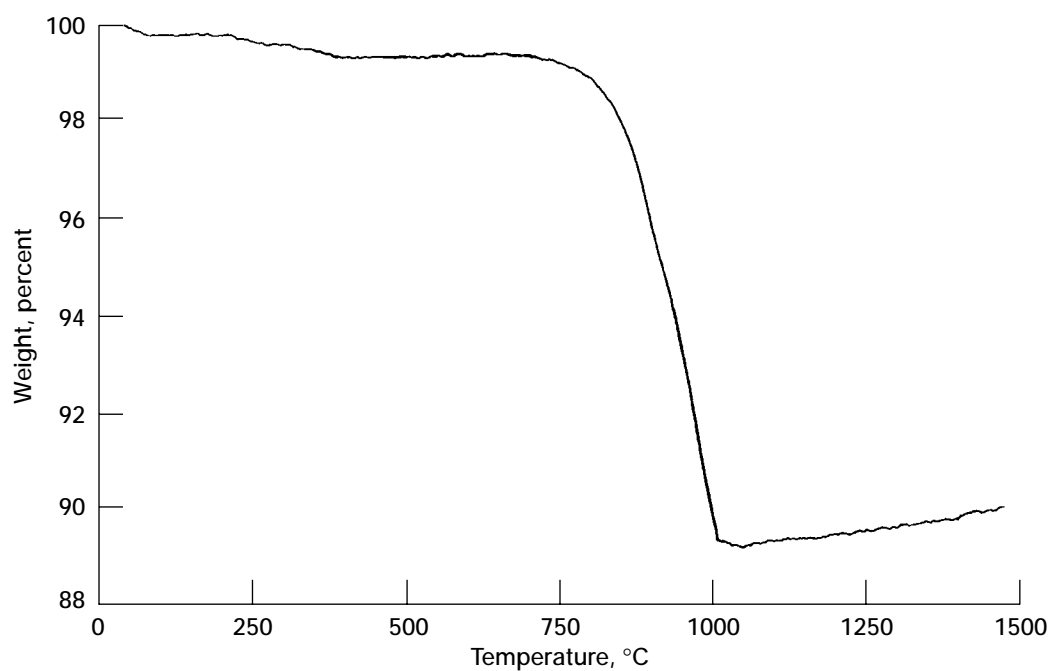


Figure 2.—TGA curve of $0.75\text{BaCO}_3\text{--}0.25\text{SrCO}_3\text{--Al}_2\text{O}_3\text{--}2\text{SiO}_2$ mixed powder at a heating rate of $5^\circ\text{C}/\text{min}$ in air.

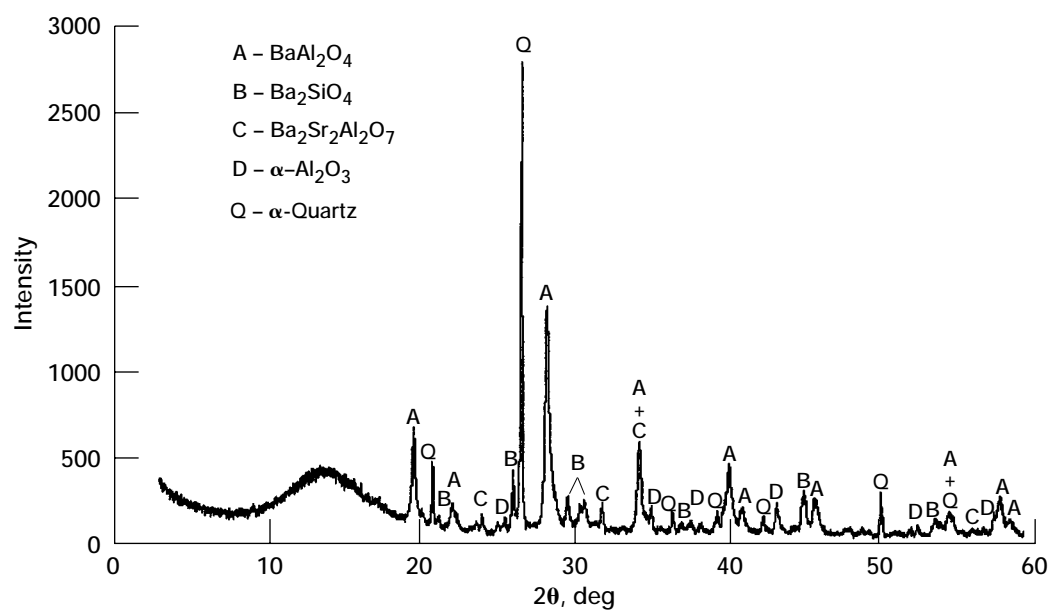


Figure 3.—Powder x-ray diffraction pattern of the mixed $0.75\text{BaCO}_3\text{--}0.25\text{SrCO}_3\text{--Al}_2\text{O}_3\text{--}2\text{SiO}_2$ powder after calcination at 915°C for 20 h in air.

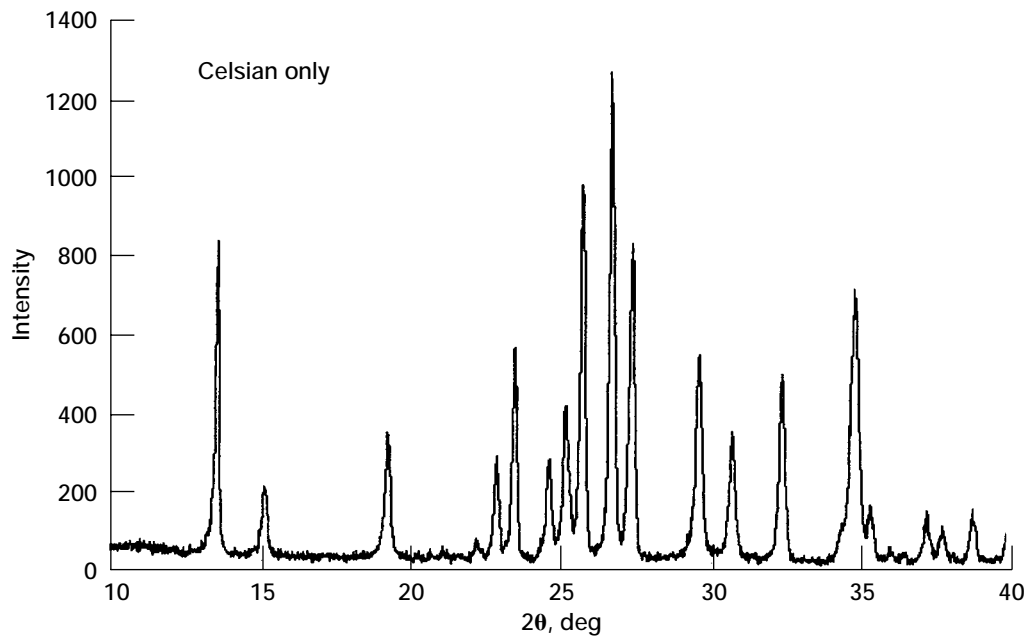


Figure 4.—X-ray diffraction spectra from the surface of a $\text{Ba}_{0.75}\text{Sr}_{0.25}\text{Al}_2\text{Si}_2\text{O}_8$ plate hot pressed at 1300 °C for 2 hr at 27.6 MPa. All the diffraction peaks match with the monoclinic celsian phase.

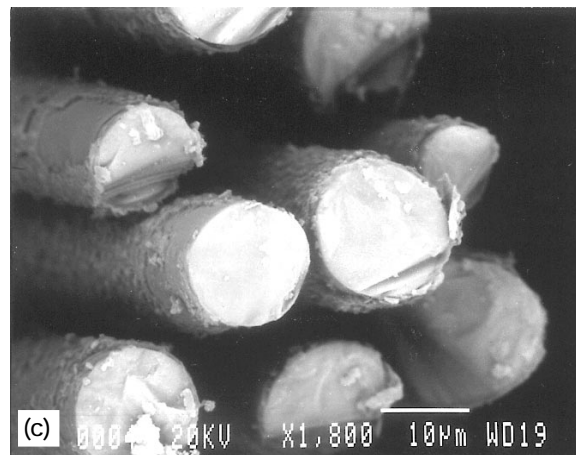
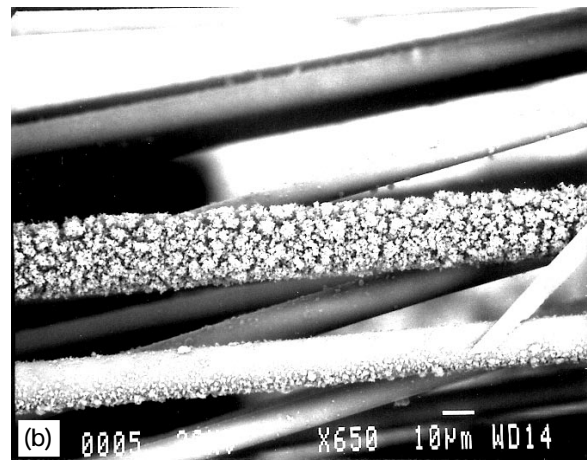
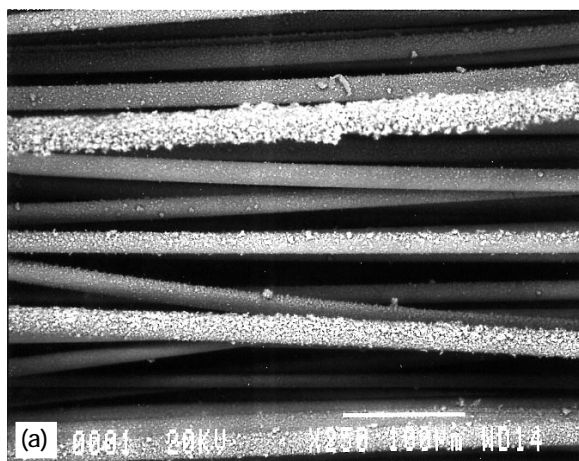


Figure 5.—SEM micrographs showing surface (a and b) and cross-section (c) of BN/SiC coated Hi-Nicalon fibers.

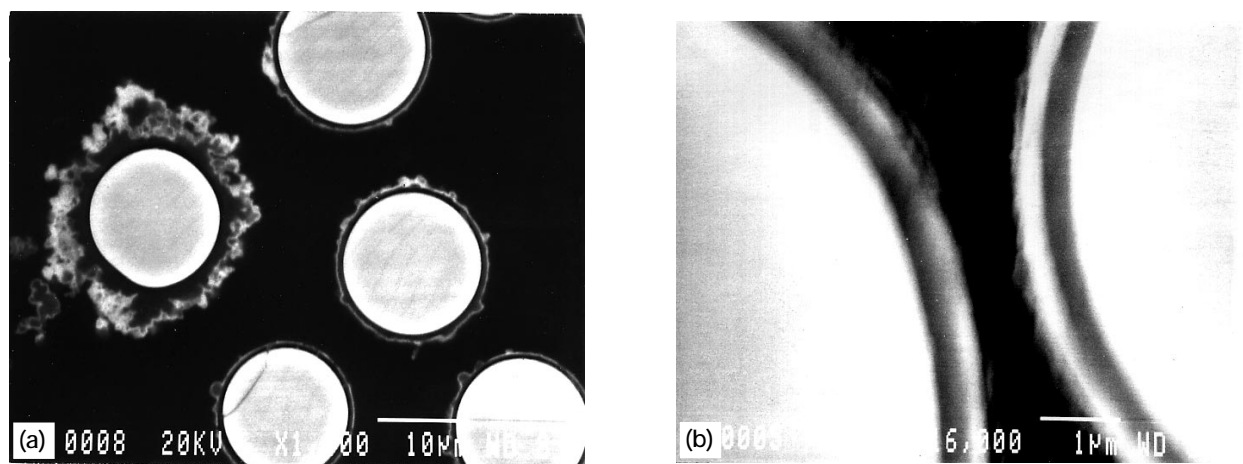


Figure 6.—SEM micrographs showing polished cross-section of Hi-Nicalon fibers with a duplex CVD BN/SiC coating. (a) Lower magnification. (b) Higher magnification.

TABLE I.—HI-NICALON FIBER-REINFORCED $\text{Ba}_{0.75}\text{Sr}_{0.25}\text{Al}_2\text{Si}_2\text{O}_8$ CELSIAN COMPOSITES (UNIDIRECTIONAL; 12 PLIES)

Sample number	Hot pressing conditions	Fiber coating	Fiber content, V_f	Density, (g/cm^3)	Phase from XRD
HI-NIC-BSAS-1-29-96	Less aggressive	BN/SiC	0.42	3.05	Monoclinic celsian
HI-NIC-BSAS-1-31-96	More aggressive	BN/SiC	0.42	3.09	Monoclinic celsian

from the polished surface of the hot pressed composite was similar to that shown in figure 3. Monoclinic celsian was the only crystalline phase present and the undesired hexacelsian phase was not detected from XRD. This implies that the desired, thermodynamically stable, monoclinic celsian phase is formed *in situ*, from the mixed oxides precursor, during hot pressing of the composite. Doping with SrO facilitates (refs. 9 and 10) the formation of monoclinic celsian in the matrix. In a recent study (ref. 17), a minor amount of hexacelsian phase has been detected in the matrix using Raman microspectroscopy.

SEM micrographs taken from the polished cross-section of the unidirectional hot pressed composite are shown in figure 7. Uniform fiber distribution and good matrix infiltration within the fiber tows is evident. Some of the filaments are of irregular shape rather than having circular cross-section. The manufacturer reports an average fiber diameter of $\sim 14 \mu\text{m}$, but a large variation in the diameter of the filaments within a fiber tow can be seen. The BN/SiC surface coating has been detached from some of the fibers during metallography or composite processing. Debonding or loss of the fiber coating may lead to adverse reactions between the fibers and the oxide matrix at high temperature resulting in strong fiber-matrix bonding.

TEM micrographs showing the fiber/matrix interface region of the Hi-Nicalon/BN/SiC/BSAS composite are presented in figure 8. The BN coating consists of four distinct layers as seen in figure 8(a). From EDS analysis, the fiber/BN interface was found to be rich in C along with the presence of Si and O. The SiC overcoating was often found to be missing from the BN/matrix interface, but was intact in this particular case. A crack running along the fiber/BN interface may also be seen. The BN coating, when viewed via the TEM, did reveal an internal reaction. Some areas show no evidence of coarsening (fig. 8(a)) while others show varying amounts of reaction. Figure 8(b) shows coarsening of three BN layers, from outside in towards the fiber, during hot pressing of the composite. However, the fiber/BN interface and the inner BN layer remain unchanged. EDS spectra obtained from the coarsened region (fig. 9(a)) show no obvious

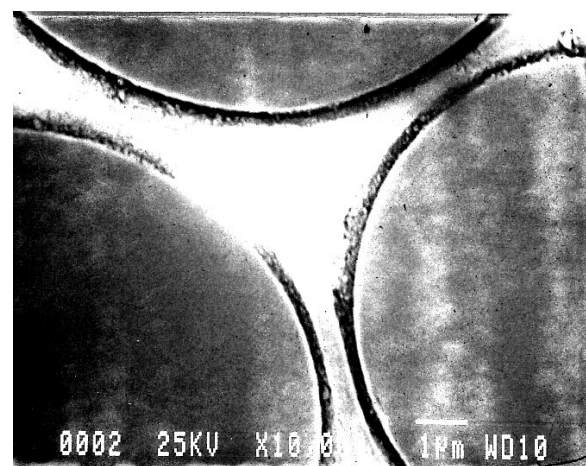
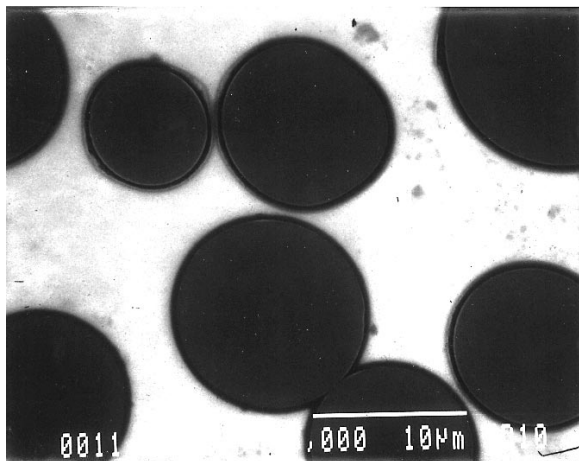
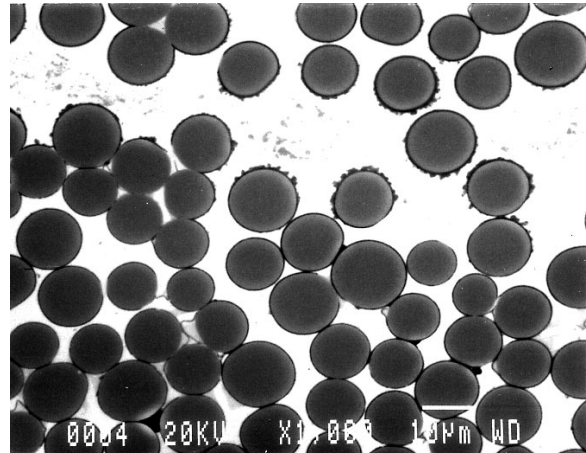
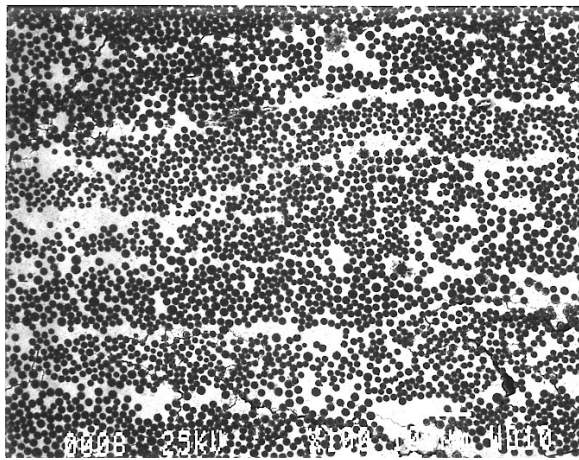


Figure 7.—SEM micrographs showing polished cross-section at different magnifications of a unidirectional Hi-Nicalon/BN/SiC/BSAS composite.

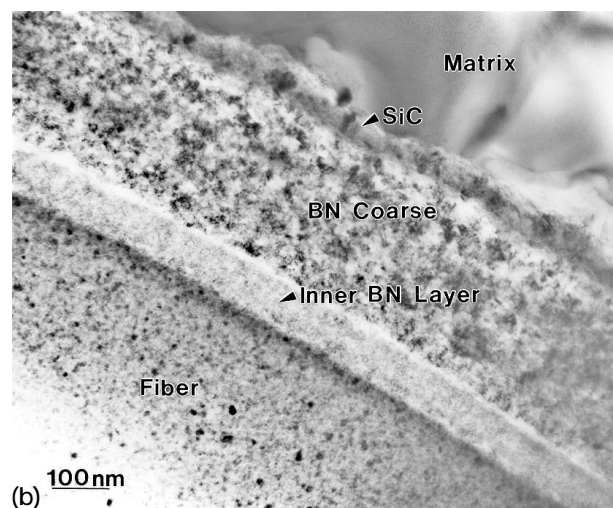
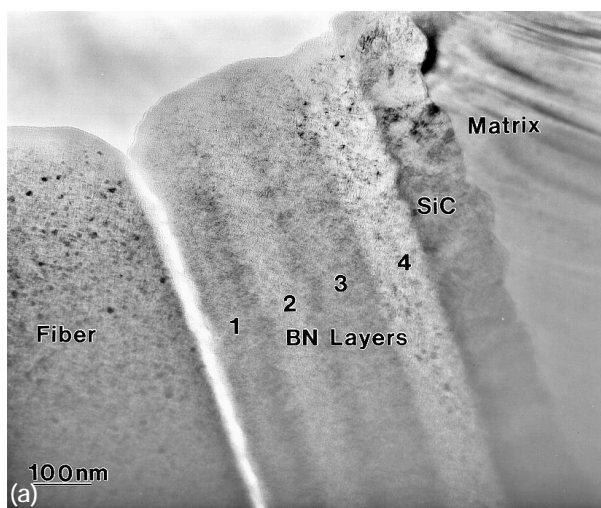


Figure 8.—TEM bright field image from cross-section of Hi-Nicalon/BN/SiC/BSAS composite showing (a) multiple BN layers and (b) coarsening of the outer three BN layers. The inner BN and the SiC interface layers are unaffected.

chemical changes in the various BN layers. Corresponding microdiffraction patterns (fig. 9(b)) show coarsening to the point where individual diffraction spots are seen. It may be pointed out that reaction through all four BN layers or visible degradation of the fiber was never observed. The SiC layer remains apparently unaffected.

Typical stress-strain curves recorded in three-point flexure for the unidirectional BSAS matrix composites reinforced with BN/SiC-coated Hi-Nicalon fibers hot pressed at two different temperatures are shown in figure 10. The fiber volume in the composites was ~42 percent. Both the composites show graceful failure. The values of yield stress, σ_y , yield strain, ϵ_y , elastic modulus, E , ultimate strength, σ_u , and ultimate strain, ϵ_u , of the composites hot pressed at two different temperatures are given in table II. Values of yield stress of 400 to 470 MPa, ultimate strength of 850 to 960 MPa and elastic modulus of 160 to 170 GPa were observed. The measured elastic modulus is in good agreement with a value of 169 GPa, calculated from the rule-of-mixtures ($E_c = V_m E_m + V_f E_f$ where V is the volume fraction and the subscripts c, m, and f refer to the composite, matrix, and fiber, respectively) using $E_m = 96$ GPa (ref. 13) and $E_f = 270$ GPa (refs. 14 and 15). Values of yield strain and the ultimate strain are ~0.26 to 0.28 percent and ~0.6 to 0.8 percent, respectively.

SEM micrographs of fracture surfaces of the two composites, after the three-point flexure tests, are shown in figure 11. Extensive long lengths of fiber pullout are observed indicating toughening behavior. An SEM micrograph of the polished cross-section of a Hi-Nicalon/BN/SiC/BSAS composite, formed under more aggressive processing conditions and flexure tested at room temperature under ambient conditions, is presented in figure 12. Debonding at the fiber-matrix interface and crack deflection around the reinforcing fibers is observed indicating a tough composite. The results of this study clearly indicate that reinforcement of BSAS matrix with Hi-Nicalon fibers having a duplex BN/SiC coating results in a strong and tough composite.

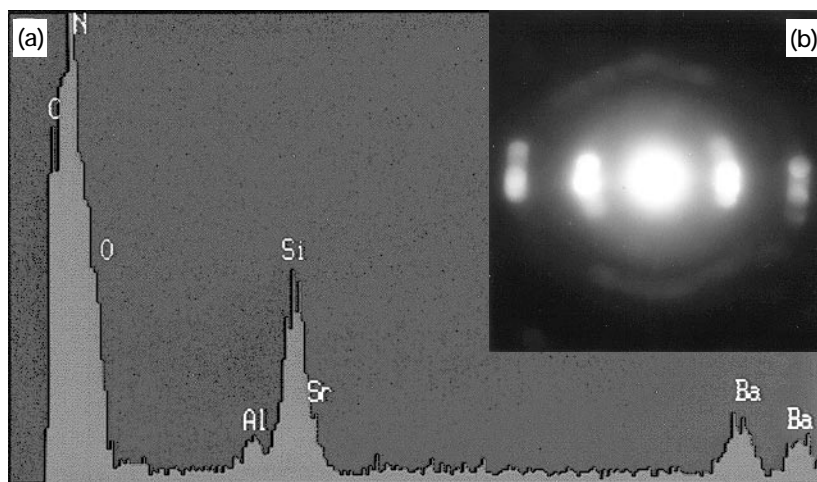


Figure 9.—EDS spectra from the coarsened BN region (a) and the corresponding microdiffraction pattern (b).

TABLE II.—ROOM TEMPERATURE MECHANICAL PROPERTIES OF HI-NICALON FIBER-REINFORCED $Ba_{0.75}Sr_{0.25}Al_2Si_2O_8$ CELSIAN COMPOSITES UNIDIRECTIONAL; 12 PLIES)

Sample number	Fiber coating	Fiber content, V_f	Elastic modulus, E (GPa)	Yield stress, σ_y (MPa)	Yield strain, ϵ_y (%)	Ultimate stress, σ_u (MPa)	Ultimate strain, ϵ_u (%)
HI-NIC-BSAS-1-29-96	BN/SiC	0.42	168	468	0.283	958	0.661
			159	405	0.258	850	0.801
HI-NIC-BSAS-1-31-96	BN/SiC	0.42	170	436	0.264	862	0.583
			165	464	0.283	960	0.771

* Measured in 3-point flexure.

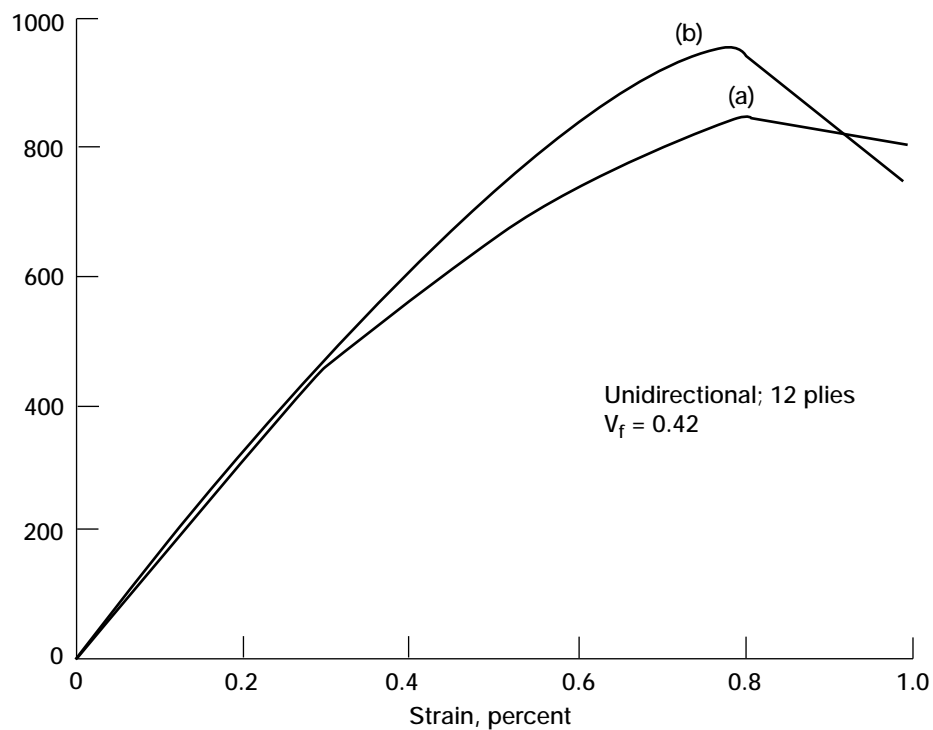


Figure 10.—Stress-strain curves recorded in 3-point flexure for unidirectional Hi-Nicalon/BN/SiC/BSAS composites hot pressed under (a) less and (b) more aggressive conditions.

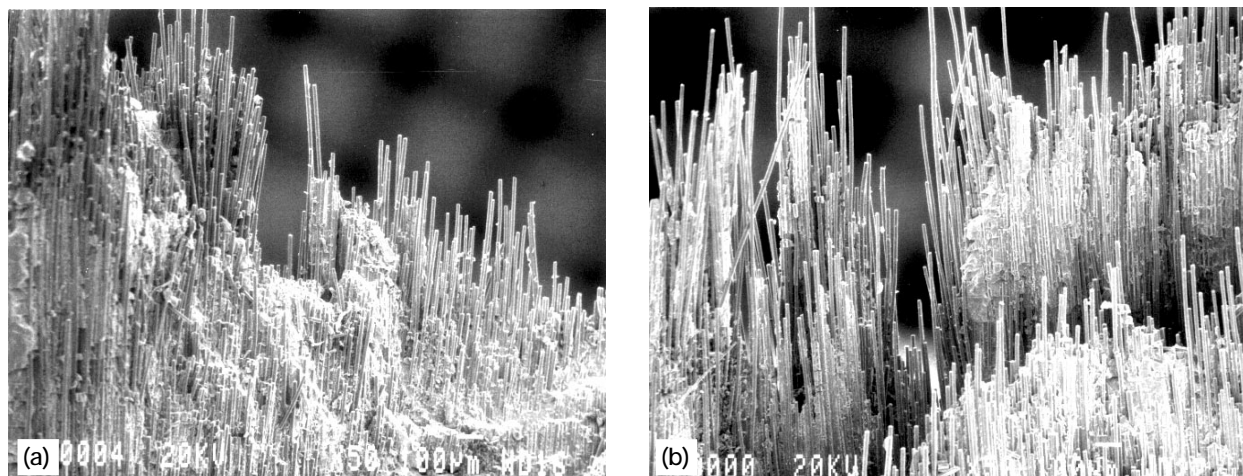


Figure 11.—SEM micrographs from the fracture surfaces of unidirectional Hi-Nicalon/BN/SiC/BSAS composites showing extensive fiber pullout; composites hot pressed under (a) less and (b) more aggressive conditions.

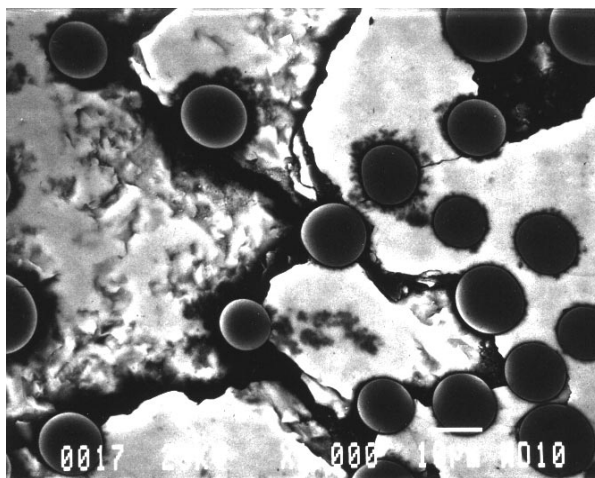


Figure 12.—SEM micrograph from the polished cross-section of a unidirectional Hi-Nicalon/BN/SiC/BSAS composite after the flexure test.

SUMMARY OF RESULTS

Hot pressing of mixed powder of $0.75\text{BaO}-0.25\text{SrO}-\text{Al}_2\text{O}_3-2\text{SiO}_2$ composition, obtained from calcination of metal carbonates and oxides, results in monoclinic celsian with complete absence of the undesirable hexacelsian phase. A method has been developed for the fabrication of small diameter multifilament tow fiber-reinforced ceramic matrix composites. BN/SiC-coated Hi-Nicalon fiber-reinforced monoclinic celsian composites have been produced by impregnation of the matrix slurry into the fiber tows, winding the tows on a drum, cutting and stacking of the prepreg tapes, and hot pressing. Strong, tough, and almost fully dense unidirectional composites having ~42 vol % of fibers were obtained. These composites exhibited graceful failure with extensive fiber pull out in a three-point flexure test. The yield stress of ~400 to 470 MPa and ultimate strength as high as 960 MPa have been observed. The yield strain was ~0.26 to 0.28 percent. The Young's modulus of the composite was measured to be ~165 GPa.

CONCLUSIONS

It may be concluded that reinforcement of the monoclinic celsian with BN/SiC-coated Hi-Nicalon fiber results in strong, tough, and almost fully dense composites.

REFERENCES

1. I.G. Talmy and D.A. Haught, Ceramics in the System $\text{BaO}.\text{Al}_2\text{O}_3.2\text{SiO}_2\text{-SrO}.\text{Al}_2\text{O}_3.2\text{SiO}_2$ for Advanced Radome Application, NSWC TE 89-162, Sept. 1989.
2. K.N. Lee, Current Status of Environmental Barrier Coatings for Si-Based Ceramics, Presented at the ICMCTF Conference, San Diego, CA, April 10-14, 2000.
3. N.P. Bansal, Ceramic Fiber Reinforced Glass-Ceramic Matrix Composite, U.S. Patent 5,214,004, May 25, 1993.
4. N.P. Bansal, Method of Producing a Silicon Carbide Fiber Reinforced Strontium Aluminosilicate Glass-Ceramic Matrix Composite, U.S. Patent 5,389,321, Feb. 14, 1995.
5. N.P. Bansal, CVD SiC Fiber-Reinforced Barium Aluminosilicate Glass-Ceramic Matrix Composites, *Mater. Sci. Eng. A*, 220, [1-2] pp. 129-139 (1996).
6. N.P. Bansal, Formation of Monoclinic Celsian in Silicon Carbide Fiber-Reinforced Barium Aluminosilicate Glass-Ceramic Matrix Composites, NASA TM-106993, August 1995.
7. Y. Takeuchi, A Detailed Investigation of the Structure of Hexagonal $\text{BaAl}_2\text{SiO}_8$ with Reference to its α - β Inversion, *Min. J. Jpn.*, 2 [5] pp. 311-332 (1958).

8. D. Bahat, Kinetic Study on the Hexacelsian-Celsian Phase Transformation, *J. Mater. Sci.*, 5, pp. 805–810 (1970).
9. N.P. Bansal and C.H. Drummond III, Kinetics of Hexacelsian-to-Celsian Phase Transformation in $\text{SrAl}_2\text{Si}_2\text{O}_8$, *J. Am. Ceram. Soc.*, 76[5], pp. 1321–1324 (1993).
10. N.P. Bansal, M.J. Hyatt, and C.H. Drummond III, Crystallization and Properties of Sr-Ba Aluminosilicate Glass-Ceramic Matrices, *Ceram. Eng. Sci. Proc.*, 12[7–8], pp. 122–21234 (1991).
11. N.P. Bansal, P. McCluskey, G. Linsey, D. Murphy, and G. Levan, Nicalon Fiber-Reinforced Celsian Glass-Ceramic Matrix Composites, Proceedings of Annual HITEMP Review, Cleveland, OH, October 23–25, 1995. NASA CP–10178, Vol. III, pp. 41–1 to 41–14 (1995).
12. N.P. Bansal, Processing and Properties of HPZ Fiber-Reinforced Celsian Glass-Ceramic Matrix Composites, in preparation.
13. N.P. Bansal, Solid State Synthesis and Properties of Monoclinic Celsian, *J. Mater. Sci.*, 33 [19], pp. 4711–4715 (1998).
14. M. Takeda, J. Sakamoto, Y. Imai, H. Ichikawa, and T. Ishikawa, Properties of Stoichiometric Silicon Carbide Fiber Derived from Polycarbosilane, *Ceram. Eng. Sci. Proc.*, 15 [4], pp. 133–141 (1994).
15. M. Takeda, J. Sakamoto, S. Saeki, Y. Imai, and H. Ichikawa, High Performance Silicon Carbide Fiber Hi-Nicalon for Ceramic matrix Composites, *Ceram. Eng. Sci. Proc.*, 16 [4], pp. 37–44 (1995).
16. K.M. Prewo, Fiber-Reinforced Glasses and Glass-Ceramics, in *Glasses and Glass-Ceramics*, Edited by M.H. Lewis, Chapman and Hall, New York, 1989, pp. 336–368.
17. G. Gouadec, P. Colomban, and N.P. Bansal, Raman Study of Hi-Nicalon Fiber Reinforced Celsian Matrix Composites. Part 1: Distribution and Nanostructure of Different Phases, to be published.

REPORT DOCUMENTATION PAGE			Form Approved OMB No. 0704-0188	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE June 2000		3. REPORT TYPE AND DATES COVERED Technical Memorandum
4. TITLE AND SUBTITLE Fabrication of Fiber-Reinforced Celsian Matrix Composites			5. FUNDING NUMBERS WU-523-31-13-00	
6. AUTHOR(S) Narottam P. Bansal and John A. Setlock				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration John H. Glenn Research Center at Lewis Field Cleveland, Ohio 44135-3191			8. PERFORMING ORGANIZATION REPORT NUMBER E-12335	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001			10. SPONSORING/MONITORING AGENCY REPORT NUMBER NASA TM-2000-210216	
11. SUPPLEMENTARY NOTES Prepared for the "Processing of Fibers and Composites" Conference, Castelvechio Pascoli, Italy, May 21-26, 2000; sponsored by the United Engineering Foundation, New York. Narottam P. Bansal, NASA Glenn Research Center and John A. Setlock, Department of Materials Science and Engineering, Case Western Reserve University, Cleveland, Ohio 44106. Responsible person, Narottam P. Bansal, organization code 5130, (216) 433-3855.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified - Unlimited Subject Category: 24 This publication is available from the NASA Center for AeroSpace Information, (301) 621-0390.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) A method has been developed for the fabrication of small diameter, multifilament tow fiber reinforced ceramic matrix composites. Its application has been successfully demonstrated for the Hi-Nicalon/celsian system. Strong and tough celsian matrix composites, reinforced with BN/SiC-coated Hi-Nicalon fibers, have been fabricated by infiltrating the fiber tows with the matrix slurry, winding the tows on a drum, cutting and stacking of the prepreg tapes in the desired orientation, and hot pressing. The monoclinic celsian phase in the matrix was produced <i>in situ</i> , during hot pressing, from the 0.75BaO-0.25SrO-Al ₂ O ₃ -2SiO ₂ mixed precursor synthesized by solid state reaction from metal oxides. Hot pressing resulted in almost fully dense fiber-reinforced composites. The unidirectional composites having ~42 vol % of fibers exhibited graceful failure with extensive fiber pullout in three-point bend tests at room temperature. Values of yield stress and strain were 435±35 MPa and 0.27±0.01 percent, respectively, and ultimate strengths of 900±60 MPa were observed. The Young's modulus of the composites was measured to be 165±5 GPa.				
14. SUBJECT TERMS Celsian; Composites; Fabrication; Mechanical properties			15. NUMBER OF PAGES 17	
			16. PRICE CODE A03	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT	